

# Substituent Effect on the Optoelectronic Properties of Alternating Fluorene-Cyclopentadithiophene Copolymers

*Bikash Pal<sup>1,3</sup>, Wei-Che Yen<sup>2</sup>, Jye-Shane Yang<sup>3</sup>, Chi-Yang Chao<sup>1</sup>, Ying-Chieh Hung<sup>4</sup>, Shiang-Tai Lin<sup>4</sup>, Chia-Hao Chuang<sup>1</sup>, Chun-Wei Chen<sup>1</sup>, and Wei-Fang Su<sup>1,2\*</sup>*

<sup>1</sup>Department of Material Science and Engineering, <sup>2</sup>Institute of Polymer Science and Engineering,

<sup>3</sup>Department of Chemistry, <sup>4</sup>Department of Chemical Engineering

National Taiwan University, Taipei, Taiwan

suwf@ntu.edu.tw

\* Corresponding Author: +886-2-3366-4078 (Fax); E-mail: suwf@ntu.edu.tw

**ABSTRACT.** A novel series of soluble alternating conjugated copolymers, comprised of 9,9-dihexylfluorene and cyclopentadithiophenes (**P1-P5**), were synthesized via Pd-catalyzed Suzuki coupling reaction in good yields. The UV-visible absorption spectra, fluorescence spectra, fluorescence quantum yields, and cyclic voltammograms of **P1-P5** are also reported. The **P2** and **P3** with electron donating non- $\pi$ -substituents (ethylenedioxy and propylenedioxy bridges the 3,3 positions of the thiophene groups) display high fluorescence quantum yields and red-shifted absorption as compared with non substituted **P1**. However, the **P4** and **P5** are weakly fluorescent and exhibit blue-shifted absorption which are due to the presence of electron-withdrawing  $\pi$ -substituents (carbonyl and dicyanoethenyl). The behavior of **P4-P5** can be attributed to the significant electronic coupling between the  $\pi$ -substituents and the conjugated polymer backbone that leads to a less allowed optical transition

between the ground and the lowest excited state, resembling the *meta* conjugation effect in phenylene-derived conjugated  $\pi$ -systems. This argument is supported by molecular orbital distribution calculations.

**KEYWORDS.** fluorene, cyclopentadithiophene, Suzuki coupling, conjugated polymer,  $\pi$ -substituent, *meta* conjugation effect.

## Introduction

The ability of chemists to design and synthesize conjugated organic copolymers remains the key to technological breakthroughs using polymers materials in electronic and photonic devices and the development of nanoscale devices. The synthesis of low band gap conjugated copolymers has been particularly rich in the recent past with the main purpose of producing polymers with high intrinsic conductivity.<sup>1</sup> An increasing interest in low band gap polymers has recently been found for applications in infrared electrochromic displays and solar cells,<sup>2-6</sup> and most of these conducting copolymers are thiophene-based.<sup>1</sup> For example, poly(cyclopentadithiophene)s and cyclopentadithiophene-based copolymers have been investigated as semiconductor layers in field effect transistors.<sup>7-10</sup> The photophysical and electrochemical properties of conjugated copolymers are primarily governed by the chemical structures of the polymer backbone. By choosing suitable functional groups attached onto the polymer main chain, it is possible to fine tune the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO) energy levels and thus alter the electronic properties. Previously, the results from a processable poly(cyanoterephthalylidene) (CN-PPV), a dialkoxy-substituted PPV derivative with cyano group on the vinylene units, have demonstrated a high internal electroluminescence quantum efficiency up to 4% in a double-layer device (ITO/PPV/CN-PPV/Al).<sup>11</sup> This improved device efficiency was attributed to better electron injection facilitated by the electron-withdrawing cyano and keto groups.

Fluorene and cyclopentadithiophene based copolymers<sup>12-17</sup> have emerged as good materials for solar cell devices. In particular, the cyclopentadithiophene derived polymers and copolymers possess the lowest known band gaps in the range from 0.16 to 1.5 eV.<sup>18-26</sup> Polycyclopentadithiophene and its

derivatives are most widely used in light absorbing diode due to their highly efficient red and infrared absorption properties in solar spectra. However, it is also known that polycyclopentadithiophene derivatives have some drawbacks such as poor solubility, excimers formation in the solid state and low charge transfer mobility. To avoid these problems, incorporation of fluorene units into the polymer chain might be a solution because polyfluorenes generally have good solubility and very good charge transfer mobility in both neutral and doped states.<sup>27</sup> In addition, thiophene-based copolymers have wide electronic tunability by changing the side chains.<sup>28,29</sup>

We report herein the synthesis of four new substituted fluorene cyclopentadithiophene alternating copolymers **P2-P5**. We have also investigated the substituent effect on the electronic properties of **P2-P5** as compared with those of the parent copolymer **P1**. While the non- $\pi$ -substituents in **P2** and **P3** reduce the band gap between the ground ( $S_0$ ) and the lowest excited state ( $S_1$ ) and have little effects on the fluorescence quantum efficiency, the electron-withdrawing  $\pi$ -substituents in **P4** and **P5** lead to band splitting and low fluorescence yields. The latter indicates the presence of electronic coupling between the  $\pi$ -substituent and the conjugated polymer backbone, resembling the *meta* conjugation effect in the phenylene-derived conjugated systems.<sup>30,31</sup> The electronic coupling effect will result in good charge separation polymer which has potential application as high efficiency solar cell sensitizer.

## Experimental Section

**General.** Reagents and chemicals were purchased from Aldrich Chemical Co. unless otherwise stated. All the new compounds were characterized by  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR and FTIR spectra. FTIR spectra were recorded on a Perkin Elmer spectrometer. NMR spectra were collected on a Bruker AVANCE 400 spectrometers with  $\text{CDCl}_3$  and  $\text{DMSO-d}_6$  as solvent and tetramethyl silane as internal standard. Melting points (M.P.) were measured on a MEL-TEMP II melting point apparatus. Molecular weights of the polymers were determined by gel permeation chromatography (GPC) on a Waters 1525 Binary HPLC Pump with polystyrene as the standard and THF as the solvent. The molecular orbital distributions of polymers were calculated using quantum mechanical package Gaussian 03<sup>32</sup> and plotted using GaussView<sup>33</sup> program. UV-visible spectra were recorded on a Perkin Elmer Lambda 35 UV/VIS

Spectrometer. The photoluminescence (PL) spectra were measured by exciting the polymer samples at 350 nm and the emission was measured with a Perkin Elmer LS 55 Luminescence Spectrometer. An integrating sphere made by Labsphere was used to measure the PL efficiencies. Solutions used to detect UV-visible spectra and PL spectra were prepared from the polymer dissolved in THF. UV-visible spectra and PL spectra in the solid state were carried out on films spin-coated onto quartz plate from chloroform solution. Cyclic voltammetry (CV) was performed on a CH Instruments 611B potentiostat/galvanostat system with a three-electrode cell in a solution of  $\text{Bu}_4\text{NPF}_6$  (0.05 M) in dichloromethane (DCM) with reversible or partly reversible oxidations and in tetrahydrofuran (THF) with reversible or partly reversible reductions at a scan rate of 100 mV/s.

**Materials.** Fluorene, 3-bromothiophene, 3-thiophenecarboxaldehyde and malono-nitrile were obtained from Aldrich Chemical Co. Detailed procedures for the monomer synthesis and spectral data are shown in the supporting information.

**General Procedure of Polymerization through the Suzuki-coupling Reaction.** To a 1:1 molar mixture of 9,9-dihexylfluorene-2,7-bis(trimethylene boronate), a dibrominated compound of thiophene derivatives and tetrakis(triphenyl-phosphine) palladium(0) [ $\text{Pd}(\text{PPh}_3)_4$ ] (1 mol %) was added into a degassed mixture of toluene [(monomer) = 0.1 M] and 2 M potassium carbonate aqueous solution (3:2 in volume). The mixture was vigorously stirred and refluxed at 115°C for 48 h under the protection of nitrogen. After cooling, the mixture was poured into the stirred mixture of methanol and deionized water (10:1). A fibrous solid was obtained by filtration. The solid was redissolved in  $\text{CHCl}_3$ , washed with water three times to remove total alkali solution, dried over anhydrous  $\text{MgSO}_4$  and evaporated. The residue was dissolved in a minimum volume of  $\text{CHCl}_3$  and poured into 10 times volume of stirred methanol. The mixture was stirred at room temperature for 2 h, filtered and dried under reduced pressure at room temperature. Yields: 57-93%.

**Poly-{2,6-(4*H*-Cyclopenta[2,1-*b*:3,4-*b'*]dithiophene)-2,7-(9,9-dihexylfluorene)}, P1.** Brown solid (Yield 91%).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ , 400 MHz, ppm):  $\delta$  7.68 (s, 2H), 7.65-7.53 (m, 4H), 7.43 (brs, 2H), 3.61 (s, 2H), 2.03 (brt, 4H), 1.10-0.89 (m, 12H), 0.79-0.61 (m, 10H).  $^{13}\text{C}$  NMR ( $\text{CDCl}_3$ , 100 MHz, ppm):  $\delta$

151.72 (2XC), 150.17 (2XC), 149.29 (2XC), 139.92 (2XC), 133.95 (2XC), 124.29 (2XC), 122.94 (2XC), 120.14 (2XC), 119.37 (2XC), 118.96 (2XC), 55.23, 40.51 (2XC), 32.20, 31.47 (2XC), 29.72 (2XC), 23.79 (2XC), 22.60 (2XC), 14.01 (2XC).

**Poly-{2,6-(4,4-ethylenedioxy-4H-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene) }, P2.** Brownish green solid (Yield 93%). <sup>1</sup>H NMR (CDCl<sub>3</sub>, 400 MHz, ppm): δ 7.72-7.60 (m, 2H), 7.58-7.43 (m, 4H), 7.27 (s, 2H), 4.41 (s, 4H), 1.99 (brt, 4H), 1.09-0.88 (m, 12H), 0.75 (t, *J* = 5.64 Hz, 6H), 0.72-0.61 (m, 4H). <sup>13</sup>C NMR (CDCl<sub>3</sub>, 100 MHz, ppm): δ 151.72 (2XC), 150.49 (2XC), 140.45 (2XC), 140.17 (2XC), 138.09 (2XC), 133.28 (2XC), 124.43 (2XC), 120.22 (2XC), 119.30 (2XC), 117.17 (2XC), 107.97, 65.45 (2XC), 55.26, 40.55 (2XC), 31.49 (2XC), 29.70 (2XC), 23.76 (2XC), 22.58 (2XC), 14.00 (2XC).

**Poly-{2,6-(4,4-propylenedioxy-4H-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene)}, P3.** Brownish black solid (Yield 92%). <sup>1</sup>H NMR (CDCl<sub>3</sub>, 400 MHz, ppm): δ 7.69-7.58 (m, 2H), 7.58-7.40 (m, 4H), 7.25 (brs, 2H), 4.39 (s, 4H), 2.15 (m, 2H), 2.00 (brt, 4H), 0.99-0.82 (m, 12H), 0.80-0.58 (m, 10H). <sup>13</sup>C NMR (CDCl<sub>3</sub>, 100 MHz, ppm): δ 152.15 (2XC), 150.63 (2XC), 144.86 (2XC), 143.03 (2XC), 140.57 (2XC), 134.55 (2XC), 124.41 (2XC), 120.60 (2XC), 119.74 (2XC), 118.86 (2XC), 101.78, 61.97 (2XC), 55.06, 40.42 (2XC), 31.48 (2XC), 29.65 (2XC), 27.39, 23.69 (2XC), 22.55 (2XC), 13.97(2XC).

**Poly-{2,6-(4H-Cyclopenta[2,1-b:3,4-b']dithiophen-4-one)-2,7-(9,9-dihexylfluorene)}, P4.** This polymer was done also from P2 by the same procedure as in reference 35 (Yield 96%). Deep green solid (Yield 73%). IR (KBr) 3399, 2926, 2855, 1707, 1607, 1459, 1434, 1311, 1123, 818 cm<sup>-1</sup>. <sup>1</sup>H NMR (CDCl<sub>3</sub>, 400 MHz, ppm): δ 7.75-7.62 (m, 2H), 7.57-7.42 (m, 4H), 7.30 (brs, 2H), 1.99 (brt, 4H), 1.11-0.90 (m, 12H), 0.77-0.58 (m, 10H). <sup>13</sup>C NMR (CDCl<sub>3</sub>, 100 MHz, ppm): δ 182.00, 152.00 (2XC), 149.52 (2XC), 148.60 (2XC), 142.36 (2XC), 141.59 (2XC), 140.18 (2XC), 124.36 (2XC), 120.47 (2XC), 119.41 (2XC), 117.16 (2XC), 55.36, 40.35 (2XC), 31.45 (2XC), 29.64 (2XC), 23.78 (2XC), 22.57 (2XC), 14.00 (2XC).

**Poly-{2,6-(4-ylidenemalononitrile-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene)}**, **P5**. This polymer was done also from **P4** by same procedure as reference 35 (Yield 59%). Deep brown solid (Yield 57%). IR (KBr) 3398, 2925, 2852, 2190, 2174, 1613, 1583, 1462, 1454, 1384, 1257, 815 cm<sup>-1</sup>. <sup>1</sup>H NMR (CDCl<sub>3</sub>, 400 MHz, ppm): δ 8.62 (brs, 2H), 7.75-7.45 (m, 4H), 7.37-7.25 (m, 2H), 2.00 (brt, 4H), 1.10-0.91 (m, 12H), 0.78-0.56 (m, 10H). <sup>13</sup>C NMR (THF-d<sub>8</sub>, 100 MHz, ppm): δ 165.25, 152.97 (2XC), 152.01 (2XC), 149.95 (2XC), 141.75 (2XC), 134.17 (2XC), 125.66 (2XC), 122.88 (2XC), 121.59 (2XC), 120.47 (2XC), 119.95 (2XC), 114.57 (2XC), 105.70, 56.51, 41.35 (2XC), 32.64 (2XC), 30.84 (2XC), 23.68 (2XC), 22.74 (2XC), 14.52 (2XC).

## Results and Discussion

**Synthesis and Characterization.** The synthetic routes of monomers are outlined in Scheme 1. The monomer **1**, 9,9-dihexylfluorene-2,7-bis(trimethylene boronate) was synthesized using fluorene as the starting material following the literature method with a good yield of 75%.<sup>34-36</sup> Bis(2-iodo-3-thienyl)methanol, bis(2-iodo-3-thienyl) ketone and 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one are intermediates to synthesize monomers **2-6**. They were synthesized using 3-bromothiophene as the starting material following the literature method.<sup>37</sup> The 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one was reduced to 4*H*-cyclopenta[2,1-b:3,4-b']dithiophene by the Huang-Minlon<sup>38</sup> method, then further brominated into monomer 2,6-dibromo-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene (**2**) with a yield 84%. The bis(2-iodo-3-thienyl)ketone was converted to bis(2-iodo-3-thienyl)-4,4-ethylenedioxy by the azeotropic method using benzene and *p*-toluenesulphonic acid in 72% yield, then further reacted to 4,4-ethylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene by Ullmann coupling reaction<sup>37</sup> using Cu powder and DMF in 95% yield. The 4,4-ethylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene can also be obtained by reacting 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one with ethylene glycol, but with a lower yield of 69%. Monomer 2,6-dibromo-4,4-ethylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene (**3**) was synthesized by direct bromination of 4,4-ethylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene with THF and NBS with a yield of 94%. The synthesis of monomer 2,6-dibromo-4,4-propylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene (**4**) is similar to monomer **3** by only

replacing the ethylene glycol to propylene glycol in the reactants and with a comparable yield. The monomer 2,6-dibromo-4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one (**5**) was synthesized by the direct bromination of 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one with THF and NBS with a yield of 95%. The 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one was reacted with malononitrile in THF to afford 4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-ylidenemalononitrile<sup>39</sup> in 65% yield, then further bromination to obtain the monomer 2,6-dibromo-4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-ylidenemalononitrile<sup>39</sup> (**6**) in 77% yield.

The polymerization reactions as shown in Scheme 2 were based on the palladium catalyzed Suzuki coupling reaction<sup>40</sup> and carried out in a mixture of toluene and aqueous potassium carbonate solution (2 M) containing 1 mol % [Pd(PPh<sub>3</sub>)<sub>4</sub>] under vigorous stirring and refluxed at 115°C for 48 h under nitrogen. Poly-{2,6-(4*H*-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene)} (**P1**), poly-{2,6-(4,4-ethylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene)} (**P2**), poly-{2,6-(4,4-propylenedioxy-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexylfluorene)} (**P3**), poly-{2,6-(4*H*-cyclopenta[2,1-b:3,4-b']dithiophen-4-one)-2,7-(9,9-dihexylfluorene)} (**P4**), and poly-{2,6-(4-ylide-nemalononitrile-4*H*-cyclopenta[2,1-b:3,4-b']dithiophene)-2,7-(9,9-dihexyl-fluorene)} (**P5**) were prepared in very good yields (57-93%). **P4** can be synthesized also by the hydrolysis of **P2** with concentrated HCl in THF with a yield of 96%. **P4** can be further reacted with malononitrile in THF to obtain **P5** in 59% yield. After purification and drying the polymers **P1**, **P2**, **P3**, **P4** and **P5** were obtained as brown solid, brownish green solid, brownish black solid, deep green solid and deep brown solid powders respectively. All these polymers are readily soluble in common organic solvents such as THF, chloroform, toluene and xylene. The weigh-average molecular weight ( $M_w$ ) and polydispersity index ( $M_w/M_n$ ) of the five polymers are given in Table 1. The chemical structures of the monomers and polymers were confirmed by <sup>1</sup>H NMR, <sup>13</sup>C NMR and FTIR spectra. The major signal of <sup>1</sup>H NMR spectra of **P1-P5** at  $\delta$  7.43,  $\delta$  7.27,  $\delta$  7.25,  $\delta$  7.30 and  $\delta$  8.62 can be assigned to the proton at position 3 on the cyclopentadithiophene ring. The specific signal of **P1** at  $\delta$  3.61 can be assigned to methylene protons at position 4 on the cyclopentadithiophene ring. The specific peak of **P2** at  $\delta$  4.41 can be

assigned to four ethylenedioxy protons at position 4 and the peaks at  $\delta$  4.39 and  $\delta$  2.15 of **P3** can be assigned to six propylenedioxy protons at position 4 on the cyclopentadithiophene ring. The  $^{13}\text{C}$  NMR signal of **P4** at  $\delta$  182.00 can be assigned to position 4 keto group (C=O) on the cyclopentadithiophene ring. The FTIR spectra show **P4** film has a strong band of carbonyl group (C=O stretching mode) at  $1707\text{ cm}^{-1}$  and also **P5** film exhibits the strong bands of the cyano group (CN stretching mode) at  $2190\text{ cm}^{-1}$  and  $2174\text{ cm}^{-1}$ . All NMR spectra of copolymers are shifted to downfield as compared to their monomer spectra due to the polymerization.

**Optical Properties.** Figure 1 and Figure 2 show the UV and PL spectra of copolymers **P1-P5** in THF respectively. Compared to **P1**, **P2** and **P3** exhibited red-shifted spectra with  $\Delta\lambda_{\text{abs}} = 26\text{-}29\text{ nm}$  and  $\Delta\lambda_{\text{fl}} = 16\text{ nm}$  respectively. The spectral shifts could be attributed to the spiro connection of the 4,4-ethylenedioxy and 4,4-propylenedioxy groups with the conjugated polymer backbone so that the lone pairs of the oxygen atoms might have certain orbital interactions with the  $\pi$ -electrons of the polymer backbone. Such kind of orbital interactions enables the oxygen atoms serve as electron donating groups to effectively lower the HOMO and thus to reduce the band gap.<sup>21</sup> In contrast, the absorption maxima for **P4** and **P5** are blue shifted along with a shoulder (**P5**) or weak band (**P4**) in the red edge. Apparently, the  $S_0 \rightarrow S_1$  transition becomes less allowed. These phenomena are reminiscent of the *meta* conjugation effect observed for aminostilbenes.<sup>31</sup> In other words, the electronic interaction between the  $\pi$ -substituents, carbonyl and dicyanoethenyl groups, and the  $\pi$ -conjugated polymer backbone resembles the case of *meta*-phenylene bridged subunits. The weak fluorescence of **P4** and **P5** (Table 2) is also consistent with the forbidden nature of optical transition between  $S_0$  and  $S_1$ . Similar spectral properties are also observed for **P1-P5** in thin solid films (Figures 3 and 4 and Table 2). We have used the intersection point of UV-vis and fluorescence spectra of **P1-P5** thin films to estimate the band gap ( $E_g$ ) of the polymers. The **P2**, **P3** exhibit a lower band gap than that of **P1** due to the spiro connection of the 4,4-ethylenedioxy and 4,4-propylenedioxy groups with the conjugated polymer backbone. The **P4** and **P5** exhibit a higher band gap than that of **P1** due to the *meta* conjugation effect to prevent the  $\pi$ -electron delocalization by carbonyl and dicyanoethenyl groups (Table 2).

To further understand the optical properties of **P4** and **P5**, we have carried out the molecular orbital distribution calculations using quantum mechanical package Gaussian 03. For comparison, the corresponding calculations on **P1** were also performed. Equilibrium geometry of the molecules in the ground state was first obtained from geometry optimization calculations using the density functional theory (DFT) with the B3LYP functional<sup>41,42</sup> and the 6-31G\* basis set. The optimized geometry was ensured to be in a minimum energy state by checking the energy second derivatives (NIMAG = 0). Note that 9,9-dimethylfluorene instead of 9,9-dihexylfluorene was used in the calculation to avoid the expensive computation demand (we have separately examined and found that the presence of alkyl side chain does not have a significant effect on the molecular orbital distribution). The HOMO-LUMO gaps ( $\Delta_{H-L}=E_{LUMO}-E_{HOMO}$ ) and main electronic transition energy (i.e., absorption energy  $E_{abs}$  having the largest oscillator strength) from ZINDO calculation<sup>43</sup> for **P1**, **P4** and **P5** are listed in Table 3. It is found that there is an excellent linear correlation between  $\Delta_{H-L}$ ,  $E_{abs}$  and the inverse of polymer chain length  $n$ . Therefore these values for the **P1**, **P4**, and **P5** with experimentally synthesized chain length are extrapolated from  $n=1, 2, 3$ , and  $4$ . It can be seen that while the HOMO-LUMO gaps of **P4** and **P5** are lower than that of **P1** as one would expect for donor-acceptor conjugate copolymers, the main photon adsorption energy (corresponding to  $\lambda_{max}$  in UV-vis experiment) for these two copolymers are higher than that of **P1**, as observed experimentally.

The detailed electronic transitions, including excitation energies, oscillator strengths  $f$ , and configurations for **P1**, **P4** and **P5** with different chain lengths are presented in Table 4. The calculated excitation energies with largest oscillator strength correspond to  $\lambda_{max}$  in UV-vis adsorption spectrum. Except for **P1** ( $n=1, 2, 3, 4$ ) and **P4** ( $n=1$ ), HOMO→LUMO transition does not play an important role in the main optical transition (i.e., transition to excited states which have the largest oscillator strength). Moreover, transition to higher excited states becomes the major transition as the chain length increases. This leads to a higher optical transition energy, or blue-shift in the UV-vis spectrum, as observed experimentally for **P4** and **P5**.

Clarke et al.<sup>44</sup> suggested that the importance of HOMO→LUMO transition may be more easily understood from the spatial distribution of molecular orbitals. It is argued that, to a first approximation, little orbital overlap between HOMO and LUMO implies a less intense transition between HOMO and LUMO. The molecular orbitals in Figure 5 show that, for **P1**, there is a significant overlap between HOMO and LUMO. However, the electron density distribution at LUMO becomes highly localized near the electron-withdrawing keto and cyano groups for **P4** and **P5**, respectively. In contrast, there is a higher degree of electron density overlapping between HOMO and LUMO+2 in **P4** and **P5**. This implies that HOMO→LUMO+2 would have more contribution to the main optical transition than the HOMO→LUMO transition would. This is consistent with the electronic transition calculation from ZINDO given in Table 3. As a consequence we observe a blue-shift in maximum absorption peak in UV-vis and fluorescence spectra for these two copolymers. Since it has recently been shown that meta-bridged electron donor-acceptor systems are potential candidates as high-efficiency solar-cell sensitizers<sup>30</sup> owing to better charge separation, the “*meta* conjugation effect” observed for **P4** and **P5** may be useful for solar cell applications.

**Electrochemical Properties.** Cyclic voltammetry (CV) experiments were conducted to probe the electrochemical properties of **P1-P5**. The voltammograms and the onset potentials of oxidation ( $E_{\text{onset, ox}}$ ) and reduction ( $E_{\text{onset, red}}$ ) are shown in Figure 6 and Table 5, respectively. All measurements were calibrated using ferrocene (Fc) value of +0.32 eV as the standard.<sup>45</sup> The HOMO and LUMO and thus the electrochemical band gaps,  $E_g = (E_{\text{LUMO}} - E_{\text{HOMO}})$ ,<sup>46,47</sup> could be estimated (Table 5) according to the empirical relationship proposed by de Leeuw et al (eq 1):<sup>48</sup>

$$I_p(\text{HOMO}) = -(E_{\text{onset, ox}} + 4.39) \text{ (eV)}, E_a(\text{LUMO}) = -(E_{\text{onset, red}} + 4.39) \text{ (eV)} \quad \text{eq 1}$$

The resulting band gaps are slightly higher than the optical bandgap (see Table 2) for **P1**, **P4** and **P5** due to interface barrier for charge injection.<sup>49</sup> However, the electrochemical band gaps of polymers **P2** and **P3** are smaller than that measured from the UV-vis spectrum, because the oxidation potential of these two polymers could not be measured exactly.<sup>29</sup> It should be noted that incorporation of the electron-deficient fluorene derivative into the polycyclopentadithiophene backbone decreases the


energy level of HOMO but increases that of LUMO, leading to a higher band gap in the copolymers (**P4**: 2.11 eV) versus the cyclopentadithiophene homopolymer (1.70 eV).<sup>39</sup>

## Conclusion


A novel series of fluorene-based conjugated polymers comprised of alternating 9, 9-dihexylfluorene and cyclopentadithiophene derivatives were synthesized via a palladium-catalyzed Suzuki coupling reaction. Efficient absorption spectra tuning and good solubility in common organic solvents are demonstrated with the changes in the backbone structures. Both the optical and electrochemical properties are all sensitive to the changes of the functional group at bridge-position on the cyclopentadithiophene ring. The behavior that resembles the *meta* conjugation effect for  $\pi$ -substituents at the bridge position might prove of values in designing new materials for the fabrication of polymer solar cells. The results have been confirmed by molecular orbital distribution calculation.

**ACKNOWLEDGMENT.** We thank the National Science Council of Taiwan supporting this research under the grant of NSC 95-2120-M- 002-012, and computation resources from the National Center for High-Performance Computing of Taiwan.


**Supporting Information Available.** Detailed procedures for the monomer synthesis and spectral data are shown in the supporting information. The material is available free of charge via the Internet at <http://pubs.acs.org>.

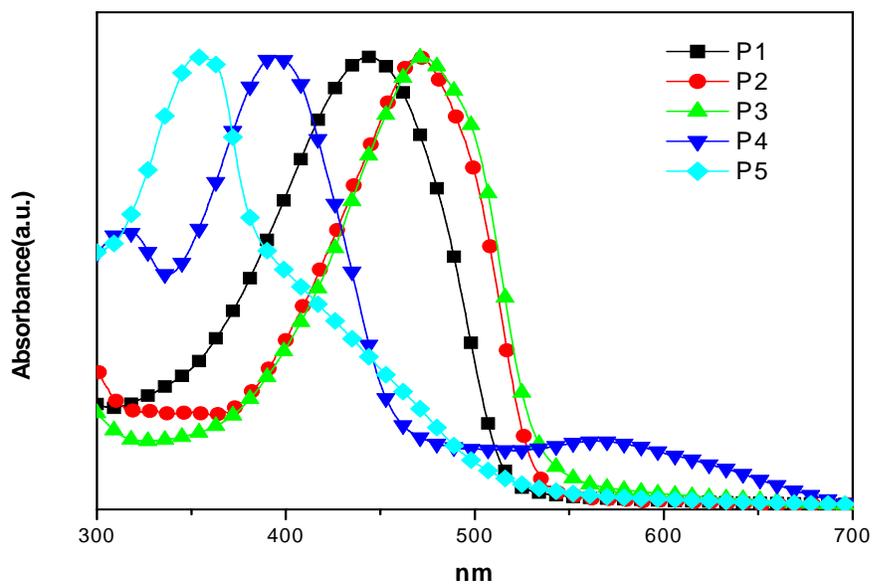


**Figure 1.** UV-visible absorption spectra of **P1**, **P2**, **P3**, **P4** and **P5** in THF solution (ca.  $1.67 \times 10^{-5}$  wt %) at room temperature

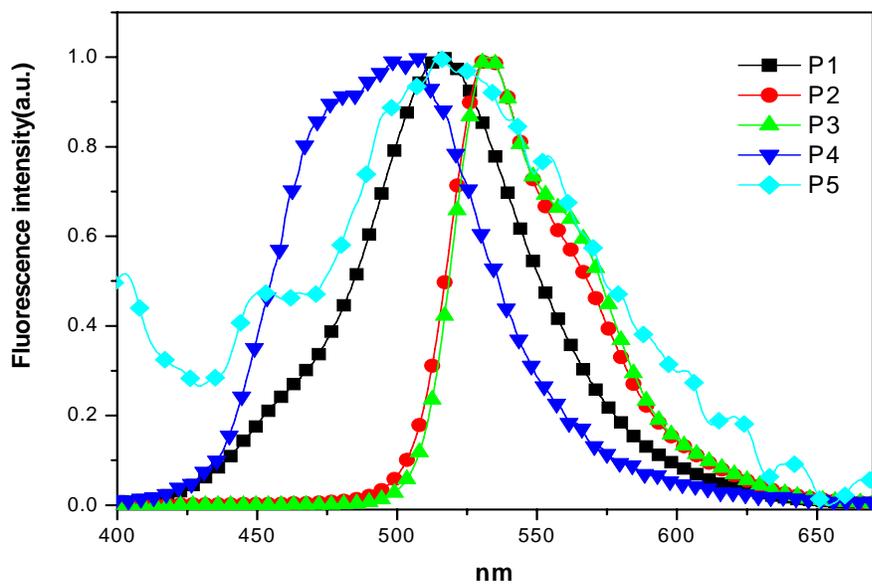

**Figure 2.** PL spectra of **P1**, **P2**, **P3**, **P4** and **P5** in THF solution (ca.  $1.67 \times 10^{-5}$  wt %) at room temperature

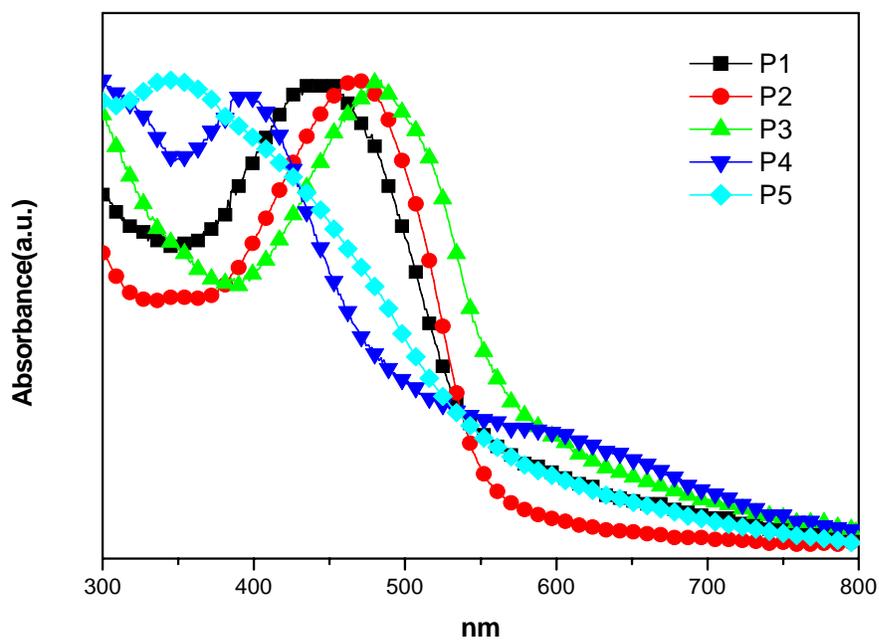


**Figure 3.** UV-visible absorption spectra of the thin film of **P1**, **P2**, **P3**, **P4** and **P5** coated onto fused quartz plate

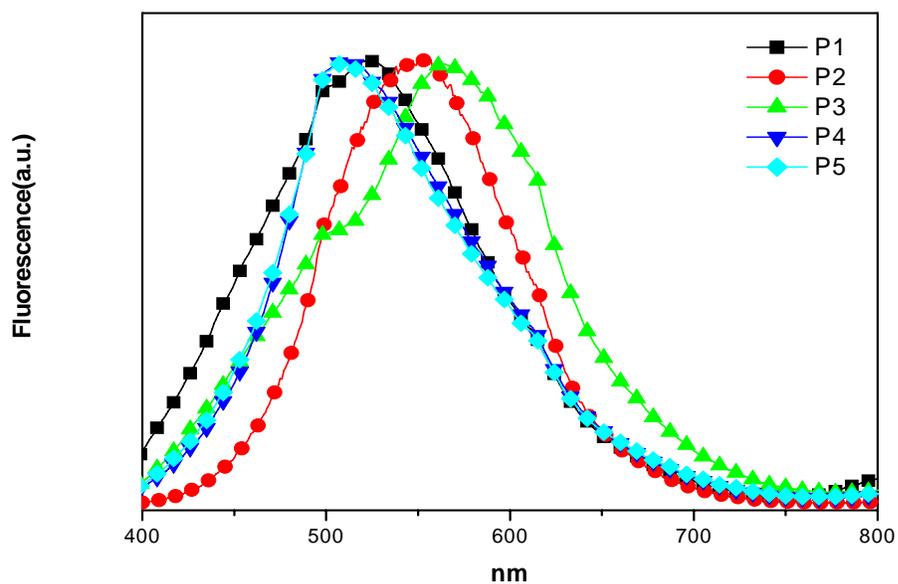


**Figure 4.** PL spectra of the thin film of **P1**, **P2**, **P3**, **P4** and **P5** coated onto fused quartz plate

**P1**

HOMO

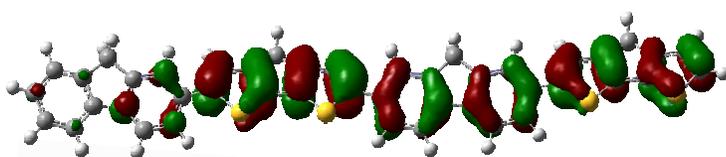


LUMO

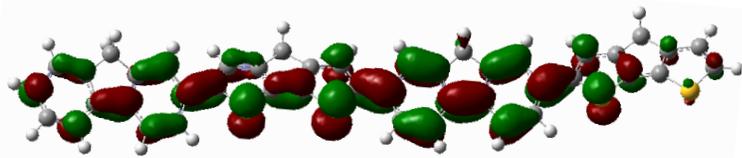


**P4**


HOMO

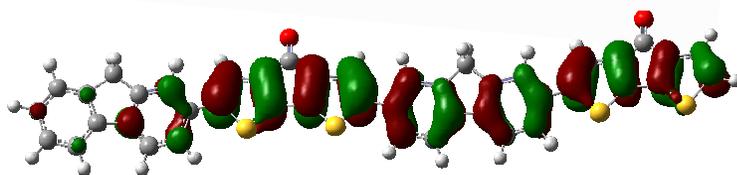

LUMO

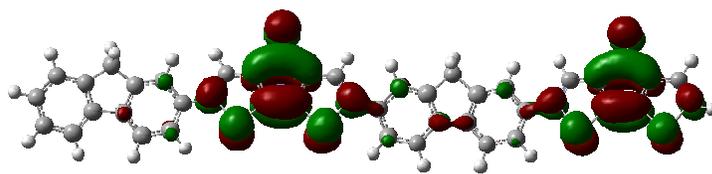


LUMO+2

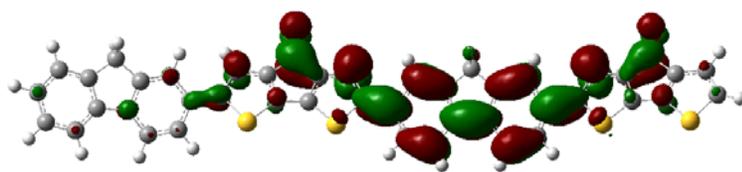


**P5**


HOMO

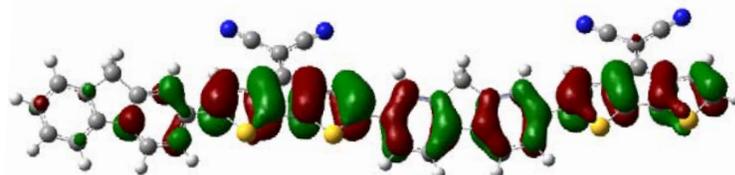


LUMO

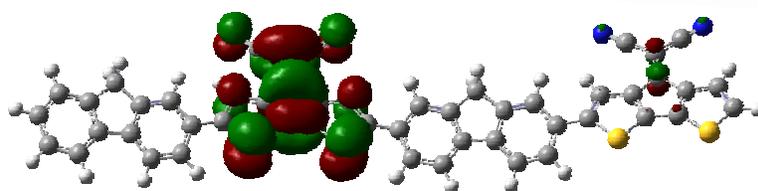

LUMO+2

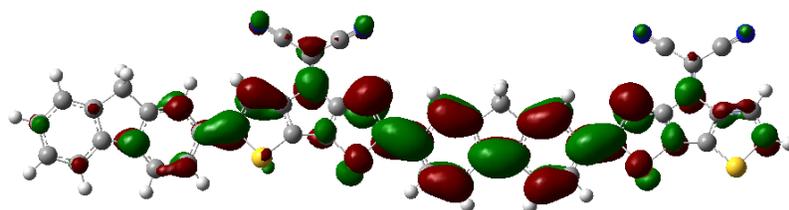


**Figure 5.** Molecular orbital HOMO and LUMO of **P1**, **P4** and **P5** with a chain length  $n=2$ .

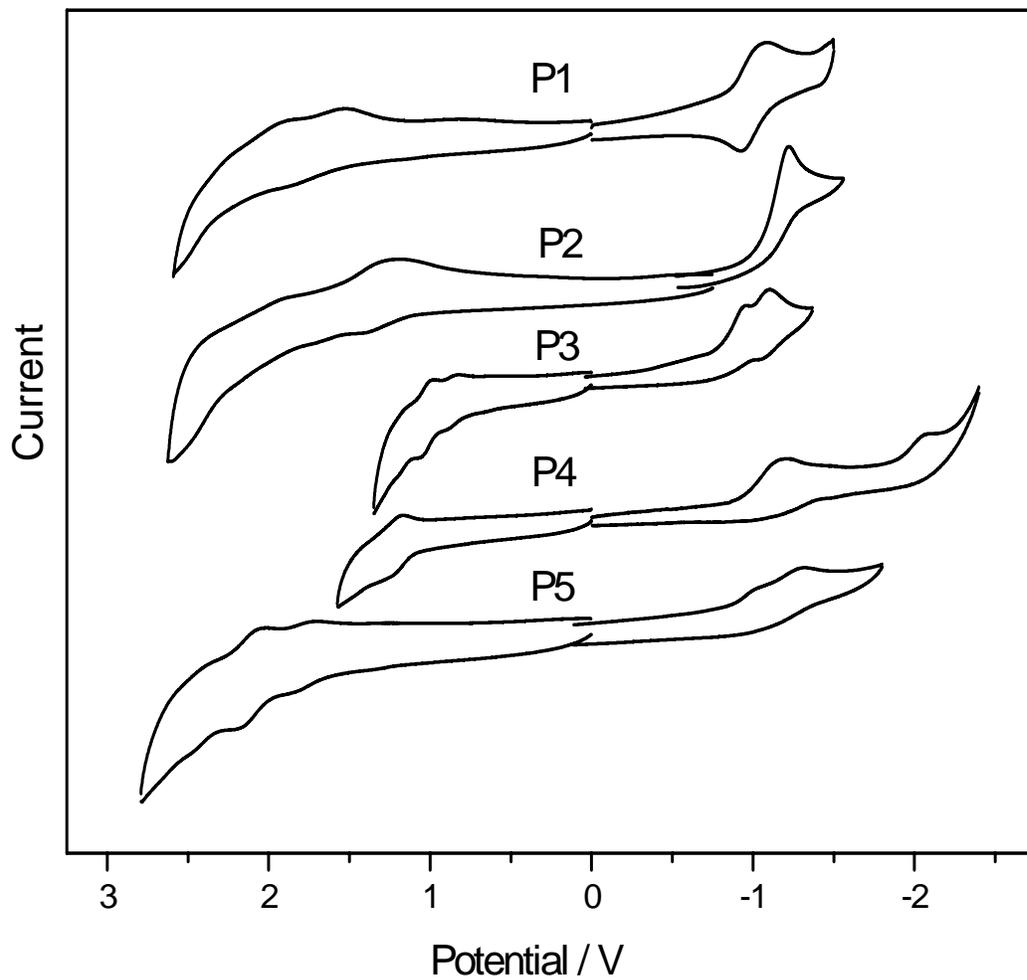

**Figure 6.** Cyclic voltammograms of the electrochemical oxidation and reduction of copolymers **P1**, **P2**, **P3**, **P4** and **P5** in 0.05 M TBAPF<sub>6</sub> in CH<sub>2</sub>Cl<sub>2</sub> and THF at a sweep rate of 100 mV/s.



**Scheme 2. Synthetic Routes for Polymers<sup>a</sup>**

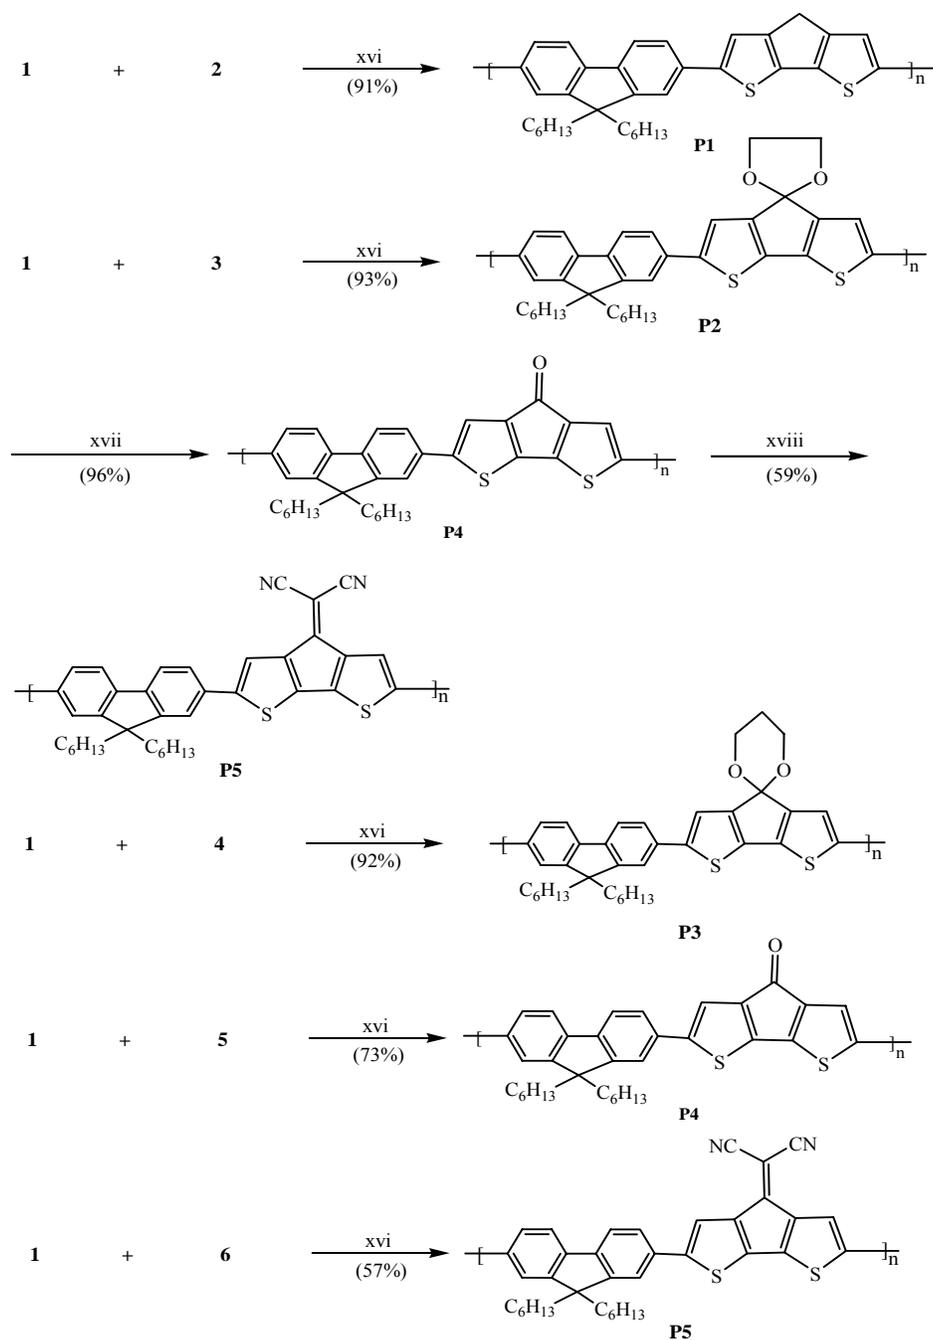

<sup>a</sup>Reagents and Conditions: xvi.  $[(PPh_3)_4]Pd(0)$  (1.0 Mol %), Toluene/2 M  $K_2CO_3$  (3:2), Reflux, 115°C, 48h, xvii. THF, Conc<sup>n</sup> HCl, 1h, xviii. THF,  $CH_2(CN)_2$ , Piperidine (cat.), Reflux, 14h.

**Table 1.** Number-Average ( $M_n$ ), Weigh-Average ( $M_w$ ) Molecular Weight, Polydispersity Index of fluorene-cyclopentadithiophene copolymers

Polymer	$M_n$	$M_w$	PDI ( $M_w/M_n$ )
P1	2688	4112	1.47
P2	3981	5833	1.46
P3	3495	4789	1.37
P4	3643	4741	1.30
P5	4292	12023	2.80

**Table 2.** Optical properties of fluorene cyclopentadithiophene copolymers

Polymer	UV-vis in THF sol <sup>n</sup> $\lambda_{\max}$ (nm)	PL in THF sol <sup>n</sup> $\lambda_{\max}$ (nm)	$\Phi_{fl}$	UV-vis in films $\lambda_{\max}$ (nm)	PL in films $\lambda_{\max}$ (nm)	Wavelength of intersection point of UV-vis and PL	$E_g$ (eV)
P1	443	516	0.40	438	523	498	2.49
P2	469	532	0.41	467	554	519	2.39
P3	472	532	0.42	484	564	539	2.30
P4	394, 586	508	<0.01	395, 589	508	649 479	2.59, 1.91
P5	353	498	0.06	345	509	484	2.56

**Table 3.** HOMO-LUMO gaps ( $\Delta_{\text{H-L}}$ ) and main electronic transition energy ( $E_{\text{abs}}$ ) for different lengths of **P4** and **P5** at the B3LYP/6-31G\* optimized geometry

n	P1(n)		P4(n)		P5(n)	
	$\Delta_{\text{H-L}}$ (eV)	$E_{\text{abs}}$ (eV)	$\Delta_{\text{H-L}}$ (eV)	$E_{\text{abs}}$ (eV)	$\Delta_{\text{H-L}}$ (eV)	$E_{\text{abs}}$ (eV)
1	3.42	2.79	2.76	2.79	2.09	3.28
2	2.87	2.48	2.38	3.18	1.81	2.99
3	2.72	2.4	2.28	3.12	1.72	2.92
4	2.65	2.37	2.24	3.1	1.69	2.88
exp <sup>a</sup>	2.50	2.28	2.12	3.05	1.58	2.76
$E_{\text{g}}(\text{exp})^{\text{b}}$	<b>2.49/2.56</b>		<b>2.59/2.11</b>		<b>2.56/2.71</b>	

<sup>a</sup>Values from linear extrapolation to the experimental molecular weight (for n=8 for P1 n=9 for **P4** and n=21 for **P5**)

<sup>b</sup>Experimentally determined band gap (Optical/Electrochemical) as shown in Tables 2 and 4

**Table 4.** Electronic transition data from ZINDO calculation for different lengths of **P1**, **P4** and **P5** at the B3LYP/6-31G\* optimized geometry

copolymers (n) <sup>a</sup>	Electronic transition	E <sub>abs</sub> (eV)	<i>f</i> <sup>b</sup>	main configurations
1(1)	S <sub>0</sub> ->S <sub>1</sub>	2.79	1.06	HOMO->LUMO(0.66)
	S <sub>0</sub> ->S <sub>4</sub>	4.18	0.15	HOMO->LUMO+1(0.15) HOMO-1->LUMO+1(0.14)
P1(2)	S <sub>0</sub> ->S <sub>1</sub>	2.48	2.16	HOMO->LUMO(0.58)
	S <sub>0</sub> ->S <sub>2</sub>	2.79	0.31	HOMO-1->LUMO+1(0.26) HOMO->LUMO+1(0.16)
P1(3)	S <sub>0</sub> ->S <sub>1</sub>	2.40	3.49	HOMO->LUMO(0.50)
	S <sub>0</sub> ->S <sub>3</sub>	2.80	0.44	HOMO-1->LUMO+1(0.34) HOMO-2->LUMO+2(0.20)
P1(4)	S <sub>0</sub> ->S <sub>1</sub>	2.37	4.70	HOMO->LUMO(0.44)
	S <sub>0</sub> ->S <sub>4</sub>	2.80	0.39	HOMO-1->LUMO+1(0.31) HOMO-2->LUMO+2(0.27)
P4(1)	S <sub>0</sub> ->S <sub>1</sub>	2.79	1.06	HOMO->LUMO(0.66)
	S <sub>0</sub> ->S <sub>4</sub>	4.18	0.15	HOMO->LUMO+1(0.15) HOMO-1->LUMO+1(0.14)
P4(2)	S <sub>0</sub> ->S <sub>5</sub>	3.18	1.84	HOMO->LUMO+2(0.42)
	S <sub>0</sub> ->S <sub>1</sub>	1.75	0.49	HOMO->LUMO+3(0.22)
	S <sub>0</sub> ->S <sub>6</sub>	3.41	0.26	HOMO-1->LUMO+4(0.20)
P4(3)	S <sub>0</sub> ->S <sub>7</sub>	3.12	2.88	HOMO->LUMO+4(0.40)
	S <sub>0</sub> ->S <sub>1</sub>	1.73	0.92	HOMO-1->LUMO+3(0.18)
	S <sub>0</sub> ->S <sub>9</sub>	3.40	0.42	HOMO->LUMO(0.17)
P4(4)	S <sub>0</sub> ->S <sub>9</sub>	3.09	3.83	HOMO->LUMO+6(0.37)
	S <sub>0</sub> ->S <sub>1</sub>	1.71	1.32	HOMO-1->LUMO+5(0.22)
	S <sub>0</sub> ->S <sub>12</sub>	3.40	0.36	HOMO->LUMO(0.16)
P5(1)	S <sub>0</sub> ->S <sub>2</sub>	3.28	1.14	HOMO->LUMO+1(0.60)
	S <sub>0</sub> ->S <sub>4</sub>	3.75	0.66	HOMO-1->LUMO(0.19) HOMO-1->LUMO+2(0.14)
P5(2)	S <sub>0</sub> ->S <sub>3</sub>	2.99	2.32	HOMO->LUMO+2(0.51)
	S <sub>0</sub> ->S <sub>8</sub>	3.74	0.67	HOMO-1->LUMO+3(0.22)
	S <sub>0</sub> ->S <sub>7</sub>	3.51	0.44	HOMO->LUMO+3(0.16)
P5(3)	S <sub>0</sub> ->S <sub>4</sub>	2.92	2.88	HOMO->LUMO+3(0.44)
	S <sub>0</sub> ->S <sub>11</sub>	3.55	0.73	HOMO->LUMO+4(0.16)
	S <sub>0</sub> ->S <sub>16</sub>	3.83	0.64	HOMO-1->LUMO+4(0.23)
P5(4)	S <sub>0</sub> ->S <sub>5</sub>	2.88	4.71	HOMO->LUMO+4(0.39)
	S <sub>0</sub> ->S <sub>15</sub>	3.57	1.06	HOMO-1->LUMO+5(0.22)
	S <sub>0</sub> ->S <sub>18</sub>	3.74	0.66	HOMO->LUMO+1(0.14)

<sup>a</sup>Number in parenthesis indicates the chain length n used in the calculation

<sup>b</sup>Oscillator strength

**Table 5.** Electrochemical properties and energy levels of fluorene cyclopentadi-thiophene copolymers

polymer	$E_{\text{Onset.Oxd}}$ (eV)	$E_{\text{Onset.Red}}$ (eV)	HOMO (eV)	LUMO (eV)	$E_g$ (eV)
P1	1.74	-0.82	6.13	3.57	2.56
P2	1.40	-0.90	5.79	3.49	2.30
P3	0.96	-0.86	5.35	3.53	1.82
P4	1.08	-1.03	5.47	3.36	2.11
P5	1.75	-0.96	6.14	3.43	2.71

## REFERENCES

1. Roncali, J. *Chem. Rev.* **1997**, *97*, 173.
2. Meng, H.; Tucker, D.; Chaffins, S.; Chen, Y.; Helgeson, R.; Dunn, B.; Wudl, F. *Adv. Mater.* **2003**, *15*, 146.
3. Sonmez, G.; Meng, H.; Wudl, F. *Chem. Mater.* **2003**, *15*, 4923.
4. Dhanabalan, A.; van Dongen, J. L. J.; van Duren, J. K. J.; Janssen, H. M.; van Hal, P. A.; Janssen, R. A. J. *Macromolecules* **2001**, *34*, 2495.
5. Wienk, M. M.; Struijk, M. P.; Janssen, R. A. J. *Chem. Phys. Lett.* **2006**, *422*, 488.
6. Wienk, M. M.; Turbiez, M. G. R.; Struijk, M. P.; Fonrodona, M.; Janssen, R. A. J. *Appl. Phys. Lett.* **2006**, *88*, 153511.
7. Lambert, T. L.; Ferraris, J. P. *J. Chem. Soc., Chem. Commun.* **1991**, 752.
8. Ferraris, J. P.; Lambert, T. L. *J. Chem. Soc., Chem. Commun.* **1991**, 1268.
9. Coppo, P.; Lurner, M. L. *Mat. Res. Soc. Symp. Proc.* **2003**, *771*, L4.9.1.
10. Coppo, P.; Cupertino, D. C.; Yeates, S. G.; Turner, M. L. *J. Mater. Chem.* **2002**, *12*, 2597.
11. Greenham, N. C.; Moratti, S. C.; Bradley, D. D. C.; Friend, R. H.; Holmes, A. B. *Science* **1993**, *365*, 628.
12. Lim, E.; Jung, B.-J.; Shim, H.-K. *Macromolecules* **2003**, *36*, 4288.
13. Liu, X.-M.; Lin, T.; Huang, J.; Hao, X.-T.; Ong, K. S.; He, C. *Macromolecules* **2005**, *38*, 4157.
14. Pei, J.; Yu, W.-L.; Ni, J.; Lai, Y.-H.; Huang, W.; Heeger, A. J. *Macromolecules* **2001**, *34*, 7241.
15. Pei, J.; Yu, W.-L.; Huang, W.; Heeger, A. J. *Chem. Commun.* **2000**, 1631.

16. Liu, B.; Niu, Y.-H.; Yu, W.-L.; Cao, Y.; Huang, W. *Synth. Met.* **2002**, *129*, 129.
17. Belletete, M.; Beaupre, S.; Bouchard, J.; Blondin, P.; Leclerc, M.; Durocher, G. *J. Phys. Chem. B* **2000**, *36*, 4288.
18. Lambert, T. L.; Ferraris, J. P. *J. Chem. Soc., Chem. Commun.* **1991**, 752.
19. Torres, D. A.; Ferraris, J. P. *Tetrahedron Lett.* **1994**, *35*, 7589.
20. Ferraris, J. P.; Henderson, C.; Torres, D.; Meeker, D. *Synth. Met.* **1995**, *72*, 147.
21. Brisset, H.; Thobie-Gautier, C.; Gorgues, A.; Jubault, M.; Roncali, J. *J. Chem. Soc., Chem. Commun.* **1994**, 1305.
22. Huang, H.; Pickup, P. G. *Chem. Mater.* **1998**, *10*, 2212.
23. Huang, H.; Pickup, P. G. *Chem. Mater.* **1999**, *11*, 1541.
24. Fusalba, F.; El Mehdi, N.; Breau, L.; Belanger, D. *Chem. Mater.* **1999**, *11*, 2743.
25. Kozaki, M.; Tanaka, S.; Yamashita, Y. *J. Org. Chem.* **1994**, *59*, 442.
26. Coppo, P.; Turner, M. L. *J. Mater. Chem.* **2005**, *15*, 1123.
27. Scherf, U.; List, E. J. W.; *Adv. Mater.* **2002**, *14*, 477.
28. Andersson, M. R.; Berggren, M.; Inganas, O.; Gustafsson, G.; Gustafsson-Carlberg, J. C.; Selse, D.; Hjertberg, T.; Wennerstrom, O. *Macromolecules* **1995**, *22*, 7525.
29. Pal, B.; Yen, W.-C.; Yang, J.-S.; Su, W.-F. *Macromolecules* **2007**, *40*, 8189.
30. Thompson, A. L.; Ahn, T.-S.; Justin Thomas, K. R.; Thayumanavan, S.; Martinez, T. J.; Bardeen, C. *J. J. Am. Chem. Soc.* **2005**, *127*, 16348..
31. Yang, J.-S.; Liau, K.-L.; Tu, C.-W.; Hwang, C.-Y. *J. Phys. Chem. A* **2005**, *109*, 6450.

32. Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Montgomery, J. A.; Jr., T. V.; Kudin, K. N.; Burant, J. C.; Millam, J. M.; Iyengar, S. S.; Tomasi, J.; Barone, V.; Mennucci, B.; Cossi, M.; Scalmani, G.; N. Rega; Petersson, G. A.; Nakatsuji, H.; Hada, M.; Ehara, M.; Toyota, K.; Fukuda, R.; Hasegawa, J.; Ishida, M.; Nakajima, T.; Honda, Y.; Kitao, O.; Nakai, H.; Klene, M.; Li, X.; Knox, J. E.; Hratchian, H. P.; Cross, J. B.; Adamo, C.; Jaramillo, J.; Gomperts, R.; Stratmann, R. E.; Yazyev, O.; Austin, A. J.; Cammi, R.; Pomelli, C.; Ochterski, J. W.; Ayala, P. Y.; Morokuma, K.; Voth, G. A.; Salvador, P.; Dannenberg, J. J.; Zakrzewski, V. G.; Dapprich, S.; Daniels, A. D.; Strain, M. C.; Farkas, O.; Malick, D. K.; Rabuck, A. D.; Raghavachari, K.; Foresman, J. B.; Ortiz, J. V.; Cui, Q.; Baboul, A. G.; Clifford, S.; Cioslowski, J.; Stefanov, B. B.; Liu, G.; Liashenko, A.; Piskorz, P.; Komaromi, I.; Martin, R. L.; Fox, D. J.; Keith, T.; Al-Laham, M. A.; Peng, C. Y.; Nanayakkara, A.; Challacombe, M.; Gill, P. M. W.; Johnson, B.; Chen, W.; Wong, M. W.; Gonzalez, C.; Pople, J. A. Gaussian 03, Revision C.02; Gaussian, Inc.: Wallingford CT, 2004.
33. Frisch, A.; Nielsen, A. B.; Holder, A. J. GaussView Users Manual; Gaussian Inc., 2000.
34. Ranger, M.; Rondeau, D.; Leclerc, M. *Macromolecules* **1997**, *30*, 7686
35. Koch, K.; Podlecech, J.; Pfeiffer, E.; Metzler, M. *J. Org. Chem.* **2005**, *70*, 3275.
36. Liu, B.; Yu, W.-L.; Lai, Y.-H.; Huang, W. *Macromolecules* **2000**, *33*, 8945.
37. Brzezinski, J. Z.; Reynolds, J. R. *Synthesis*, **2002**, 1053.
38. Coppo, P.; Cupertino, D. C.; Yeates, S. G.; Turner, M. L. *Macromolecules*, **2003**, *36*, 2705.
39. Berlin, A.; Zotti, G.; Zecchin, S.; Schiavon, G.; Vercelli, B.; Zanelli, A. *Chem. Mater.* **2004**, *16*, 3667.
40. Suzuki, A.; Miyaura, N. *Chem. Rev.* **1995**, *95*, 2457.
41. Becke, A. D. *Journal of Chemical Physics* **1993**, *98*, 5648.

42. Lee, C. T.; Yang, W. T.; Parr, R. G. *Physical Review B* **1988**, *37*, 785.
43. Foresman, J. B.; Headgordon, M.; Pople, J. A.; Frisch, M. J. *J. Phys. Chem.* **1992**, *96*, 135.
44. Clarke, T. M.; Gordon, K. C.; Officer, D. L.; Hall, S. B.; Collis, G. E.; Burrell, A. K. *J. Phys. Chem. A* **2003**, *107*, 11505..
45. Pommerehe, J.; Vestweber, H.; Guss, W.; Mahrt, R. F.; Bassler, H.; Porsch, M.; Daub, J. *Adv. Mater.* **1995**, *7*, 55.
46. Pei, J.; Yu, W.-L.; Huang, W.; Heeger, A. J. *Macromolecules* **2000**, *33*, 2462.
47. Chen, Z.-K.; Huang, W.; Wang, L.-H.; Kang, E.-T.; Chen, B. J.; Lee, C. S.; Lee, S. T. *Macromolecules* **2000**, *33*, 9015.
48. de Leeuw, D. M.; Simenon, M. M. J.; Brown, A. R.; Einerhand, R. F. F. *Synth. Met.* **1997**, *87*, 53.
49. Janietz, S.; Bradley, D. D. C.; Grell, M.; Giebeler, C.; Inbasekaran, M.; Woo, E. P. *Appl. Phys. Lett.* **1998**, *73*, 2453.

## SYNOPSIS TOC

### Substituent Effect on the Optoelectronic Properties of Alternating Fluorene-Cyclopentadithiophene Copolymers

Bikash Pa1, Wei-Che Yen, Jye-Shane Yang, Chi-Yang Chao, Ying-Chieh Hung, Shiang-Tai Lin,  
Chia-Hao Chuang, Chun-Wei Chen, and Wei-Fang Su\*

